

TEST REPORT

No. : NBIN1606006438PS

Date : Jul 08, 2016

Page: 1 of 3

CUSTOMER NAME: CHANGZHOU HUISU QINYE PLASTIC GROUP
ADDRESS: ROOM 1302-1303,NO.6 PENG XIN LI DU,ZHONGLOU DISTRICT
JIANGSU PROVINCE,CHINA.

The following sample(s) was/ were submitted and identified on behalf of the client as:

Sample Name : PVC SHEET
Product Specification : 18mm/20mm , density 0.52
Manufacturer : CHANGZHOU HUISU QINYE PLASTIC GROUP
Date of Receipt : Jun 29, 2016
Testing Start Date : Jun 29, 2016
Testing End Date : Jul 08, 2016
Test result(s) : For further details, please refer to the following page(s)

Signed for
SGS-CSTC Standards Technical
Services Co., Ltd Ningbo Branch



Lorin Yan
Authorized signatory



Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.
Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com
1-2,5F West No. 4 Building, Lingyun Industry Park, No. 1177 Lingyun Road, Ningbo National Hi-Tech Zone, Ningbo, China 315040 t (86-574) 87767006 f (86-574) 87901159 www.sgs.com.cn
中国·宁波·国家高新区凌云路1177号凌云产业园4号楼西1-2,5层 邮编: 315040 t (86-574) 87767006 f (86-574) 87901159 e sgs.china@sgs.com

TEST REPORT

No. : NBIN1606006438PS

Date : Jul 08, 2016


Page: 2 of 3

Summary of Results:

No.	Test Item	Test Method	Result	Conclusion
1	Flexural Strength	ISO 1209-2:2007	16400 kPa	/
2	Face withdrawal of screws	With reference to ISO 27528:2009	See test result	/

Note: Pass : Meet the requirements;
Fail : Does not meet the requirements;
/ : Not Apply to the judgment.

Original Sample Photo:

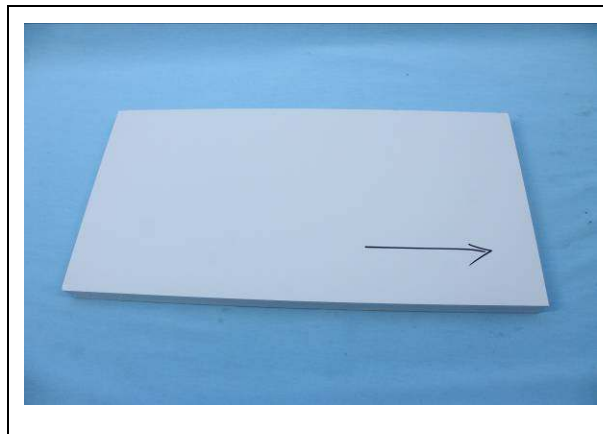

Unless otherwise agreed in writing, this document is issued by the Company subject to its General Conditions of Service printed overleaf, available on request or accessible at <http://www.sgs.com/en/Terms-and-Conditions.aspx> and, for electronic format documents, subject to Terms and Conditions for Electronic Documents at <http://www.sgs.com/en/Terms-and-Conditions/Terms-e-Documents.aspx>. Attention is drawn to the limitation of liability, indemnification and jurisdiction issues defined therein. Any holder of this document is advised that information contained hereon reflects the Company's findings at the time of its intervention only and within the limits of Client's instructions, if any. The Company's sole responsibility is to its Client and this document does not exonerate parties to a transaction from exercising all their rights and obligations under the transaction documents. This document cannot be reproduced except in full, without prior written approval of the Company. Any unauthorized alteration, forgery or falsification of the content or appearance of this document is unlawful and offenders may be prosecuted to the fullest extent of the law. Unless otherwise stated the results shown in this test report refer only to the sample(s) tested and such sample(s) are retained for 30 days only.

Attention: To check the authenticity of testing /inspection report & certificate, please contact us at telephone: (86-755) 8307 1443, or email: CN.Doccheck@sgs.com

SGS-CSTechnical Services Co., Ltd.
Ningbo Branch

1-2,5F West No. 4 Building, Lingyun Industry Park, No. 1177 Lingyun Road, Ningbo National Hi-Tech Zone, Ningbo, China 315040 t (86-574) 87767006 f (86-574) 87901159 www.sgs.com.cn
中国·宁波·国家高新区凌云路1177号凌云产业园4号楼西1-2,5层 邮编: 315040 t (86-574) 87767006 f (86-574) 87901159 e sgs.china@sgs.com

TEST REPORT

No. : NBIN1606006438PS

Date : Jul 08, 2016

Page: 3 of 3

1. Test Item: Flexural Strength

Test Method: ISO 1209-2:2007

Test Condition:

Specimen: 350 mm×72.31 mm×17.98 mm

Testing speed: 100 mm/min

Span: 300 mm

Lab Environmental Condition: 23±2°C, 50±5%RH

Test Result:

Test Item	Test Result
Flexural Strength	16400 kPa

Note: Test specimens were cut from the sample.

2. Test Item: Face withdrawal of screws

Test result:

Test item	Test method	Test condition	Withdrawal Strength (N)	
			Individual value	Average value
Face withdrawal of screws	With reference to ISO 27528:2009	Thread diameter of screw: 4.2mm Diameter of lead hole: 2.6mm Penetrate into depth: 11mm Test rate: 5mm/min	530	540
			530	
			540	
			530	
			560	
Remark	Specimen dimensions: 75mm×50mm×18mm, 5pcs, cut from original sample			

- All above tests were carried out by a SGS laboratory.

***** End of report*****

